

COLLOIDAL BISMUTH NANOPARTICLES: SYNTHESIS AND UV-VIS ABSORPTION

J. FANG, K. L. STOKES, W. L. ZHOU, J. A. WIEMANN, J. DAI, C. J. O'CONNOR

Advanced Materials Research Institute, University of New Orleans, New Orleans, LA 70148

E-mail: jfang1@uno.edu

Quantum-confined Bi structures (quantum wells and quantum wires) are currently being studied for their various novel properties. We now pursue the next level of quantum confinement in bismuth, quantum dots. In this work, we present a technique for the synthesis of bismuth nanoparticles using an inverse microemulsion method. To prevent air-oxidation in the characterization stage, poly(vinylpyrrolidone) was used as protecting agent. Our characterizations reveal that single rhombohedral phase of bismuth can be formed with ultrafine particle in size by following this synthetic route. The optical absorption spectrum of the aqueous nanoparticle colloids shows an absorption band centered at ~268 nm.

1 Introduction

The semimetal bismuth is an interesting material for electronics because of its highly anisotropic electronic behavior, low conduction-band effective mass and high electron mobility [1]. It has been reported that a conversion from a semimetal to a semiconductor could occur in thin Bi layer grown by molecular beam epitaxy [2]. This size-induced semimetal to semiconductor transition and related quantum confinement effect are potentially useful for certain optical and electro-optical device applications [3]. It has also been suggested that the nanoscale bismuth system is attractive as a potential thermoelectric material [4]. Previously, we have successfully prepared nanometer-sized bismuth using an inverse microemulsion method coating with *in-situ* polymerization [5]. In this paper, the emphasis lies in a development of colloidal synthesis route in producing bare nanometer-sized bismuth particles. The particle morphology and optical property of as-prepared sample are discussed as well.

2 Experimental Procedure

2.1 Chemicals

The starting materials used in this study include bismuth (III) citrate (>99.99% in purity), sodium borohydride (99.0% in purity), poly (oxyethylene)₉ nonyl phenol ether (hereafter NP9), polyvinylpyrrolidone (hereafter PVP, Mw ≈ 29 000), all above chemicals were from Aldrich, US); petroleum ether (b.p. 60 – 80 °C, from Fluka and packed in Switzerland), ammonia solution (concentration: 28.0 - 30.0

wt%, GR solution from EM Science), and poly (oxyethylene)₅ nonyl phenol ether (hereafter NP5, from Albright and Wilson Asia Pte Ltd, Singapore). All the solvents were Ar-degassed before use.

2.2 Preparation of Nanometer-sized Bismuth Powder

Surfactants NP5 and NP9 were pre-mixed in a weight ratio of 8:1. An inverse microemulsion system consisting of 60.30 wt% petroleum ether, 28.20 wt% mixed surfactant (NP5+NP9) and 11.50 wt% aqueous solution of 0.50 M NaBH₄ in 1.00M NH₃•H₂O was subsequently established. Another ternary system containing 60.30 wt% petroleum ether, 28.20 wt% mixed surfactant (NP5+NP9) and 11.50 wt% aqueous solution of 0.10 M bismuth (III) citrate in 1.00M NH₃•H₂O was simultaneously prepared as well. The Bi-containing system was then titrated at a rate of ~30 drops per minute into the microemulsion system while vigorously stirring. The resulting nano-bismuth powder was initially separated by a high-speed centrifugation, and was eventually retrieved by repeatedly washing away the oil and surfactant using ethanol, followed by centrifugal recovery and vacuum drying. All the above operations were performed under a nitrogen atmosphere in a glove box.

2.3 Characterizations

The as-prepared bismuth powder was dispersed into distilled water in a capped quartz cell under nitrogen and its optical density was measured using a Cary UV-Vis spectrophotometer (Cary Varian Optical Spectroscopy Instruments). To avoid possible aggregation, the sample was mechanically re-dispersed using an ultrasonic source before the measurement. A drop of the resulting solution was dried onto a carbon coated TEM grid and a JEOL 2010 transmission electron microscope was employed to observe the particle morphology. Phase identification was performed at room temperature using a (CuK_α) X-ray diffractometer (Philips X'pert Systems). To prevent from the formation of oxides, bismuth sample for XRD measurement was coated with PVP (M_w = 29 000) by re-dispersing the powder into a PVP solution in ethanol (Bismuth: PVP ≈ 1:1 in weight ratio) under nitrogen and vacuum drying.

3 Results and Discussion

3.1 Phase Identification

To identify bismuth nanoparticles prepared from the reverse microemulsion method, an XRD phase analysis was performed. The sample was pre-coated using PVP polymer to avoid an oxidation during the determination processing. Figure 1

illustrates the XRD pattern of as-prepared bismuth, showing a highly crystallized rhombohedral bismuth phase. All the major peaks are labeled and attributed to the formation of rhombohedral bismuth according to the standard ICDD PDF (Card No. 05-0519). Crystalline size was determined by applying the Scherrer equation [6] to the line broadening of the (012), (110) and (202) peaks, i.e.

$$D = 57.3 * kl / (b \cos q)$$

where k is particle shape factor (taken as 0.9), l the wave length of $\text{CuK}_{\alpha 1}$ radiation (1.54056\AA), b the calibrated half intensity width of the selected diffraction peak (degrees), q the Bragg angle (half of the peak position angle), D the crystallite size (\AA), and the factor 57.3 is used to convert b in degree to radian measure. From this equation, the average size of bismuth crystallites of the sample was estimated to be ~ 13.3 nm.

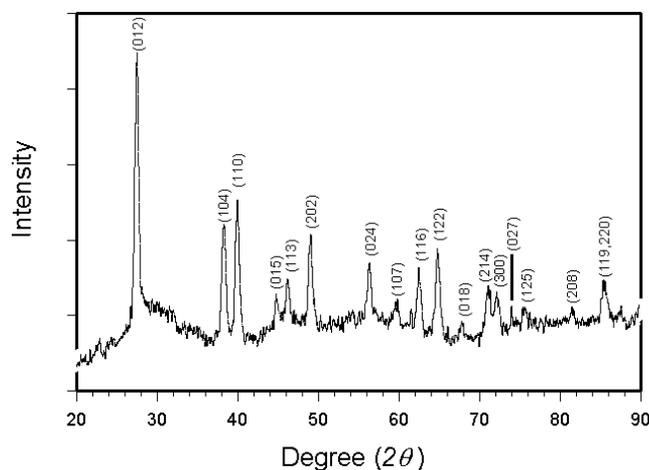


Figure 1. XRD traces of the bismuth nanoparticles prepared via the reverse microemulsion method.

3.2 Particle Morphology

Figure 2 is TEM micrograph further showing the morphology of as-prepared bismuth nanoparticles. To prevent air-oxidation, the sample dropped onto a carbon coated TEM grid was pre-coated by adding PVP-ethanol solution under nitrogen. This micrograph reveals that the bismuth particles formed in the presence of PVP prepared through this synthetic route are shaped spherically. The size of particles

is in the range about 20 nm in diameter. Although the particle edges are ambiguous, which is probably due to the presence of polymer and polymer-caused aggregation of particles, a lattice image can still be clearly detected as shown in Figure 2 (top-right).

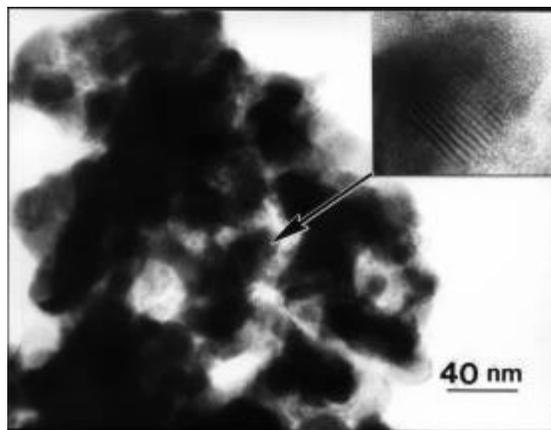


Figure 2. Transmission electron micrograph of bismuth nanoparticles prepared via the reverse microemulsion method. The top-right micrograph is an enlarged lattice image.

3.3 Optical Absorption

Figure 3 (a) is an UV absorption spectrum of pure nanometer-sized bismuth in water. It is believed that the residue of the surfactant(s) has been efficiently removed by repeatedly washing the colloidal particles before the powder was dried as described above. This spectrum was mathematically resolved into two contributions from water (curve 1) and nanometer-sized bismuth (curve 2) as indicating in Figure 3 (b). It thus reveals that the absorption peak is centered at ~268 nm. M. Gutiérrez et al. [7] previously reported that nanometer-sized bismuth particles exhibited an absorption at ~253 nm, supported by a γ -radiolysis of BiOClO_4 experiment. According to the calculation result done by J. A. Creighton et al. [8], the first absorption band of 10 nm bismuth particles should appear around 270 - 280 nm. Our result is between the above two literature values.

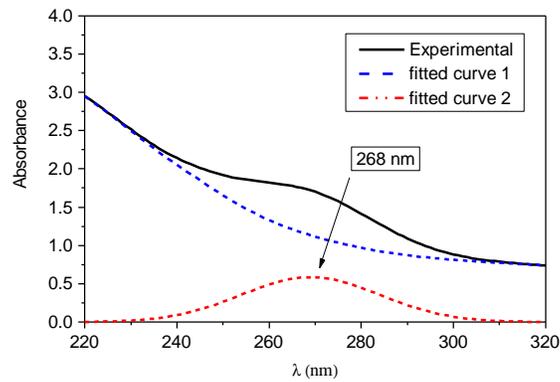
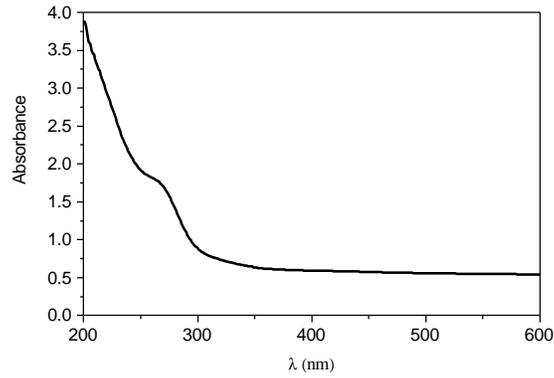


Figure 3. UV absorption spectrum of nanometer-sized bismuth aqueous solution. ((a)—top fig: the real experimental spectrum; (b)—bottom fig: resolved curves).

4 Conclusions

Nanometer-sized particles of bismuth have been synthesized by an inverse microemulsion method. X-ray diffraction data and TEM image indicate that a single rhombohedral phase of bismuth can be obtained with a nanometer-sized

crystal structure. The optical absorption spectrum of the nanoparticle colloids shows an absorption band at ~268 nm when water is used as solvent. In addition, the oxidation problem during the stage of subsequent characterization can be eliminated by using a PVP polymer technique. This also demonstrates a feasible route to produce single phase, air-sensitive metal nanocrystallites.

5 Acknowledgements

This work was supported by research grant DAAD19-99-1-0001 from the Army Research Office. We would like to thank the Chemistry Department for the use of the UV-Vis spectrophotometer. We also appreciate Dr Poncho DeLeon for his useful advice.

References

1. Gallo C. F., Chandrasekhar B. S. and Sutter P. H., Transport properties of bismuth single crystals, *J. Appl. Phys.*, **34** (1963) pp.144 - 152.
2. Hoffman C. A., Meyer J. R., Bartoli F. J., Venere A. D., Yi X. J., Hou C. L., Wang H. C. and Ketterson J. B., Semimetal-to-semiconductor transition in bismuth thin films, *Phys. Rev.* **B48** (1993) pp. 11431-11434; Reply to “comment on ‘semimetal-to-semiconductor transition in bismuth thin films’”, **51** (1995) pp. 5535 - 5337.
3. Golding T. D., Dura J. A., Wang H., Zborowski J. T., Vigliante A., Chen H. C., Miller J. H., Jr. and Meyer J. R., *Semicond. Sci. Technology*, **8** (1993) pp. S117.
4. Dresselhaus M. S., Zhang Z., Sun X., Ying J., Heremans J. P., Dresselhaus G. and Chen G., in “*Thermoelectric materials 1998, Mat. Res. Soc. Symp. Proc. 545*”, Ed. By Tritt T. M. et al., (1999) pp. 215.
5. Fang J., Stokes K. L., Wiemann J. A. and Zhou W., Nanocrystalline bismuth synthesized via an *in-situ* polymerization-microemulsion process, *Mater. Lett.*, (1999), in press.
6. H. P. Klug and L. E. Alexander, “X-ray Diffraction Procedures for Polycrystalline and Amorphous Materials”, Wiley, New York, (1954), pp. 512.
7. Gutiérrez M. and Henglein A., Nanometer-sized Bi particles in aqueous solution: absorption spectrum and some chemical properties, *J. Phys. Chem.*, **100** (1996) pp. 7656 – 7661.
8. Creighton J. A. and Desmond G. E., Ultraviolet-visible absorption spectra of the colloidal metallic elements, *J. Chem. Soc. Faraday Trans.*, **87(24)** (1991) pp. 3881 – 3891.